



# CONCRETE TECHNOLOGY

## تكنولوجيا الخرسانة 2

المرحلة الثالثة

*Asst. Lec. Nora AL-Anssari*



# Lecture 3:C

## **FACTORS AFFECTING THE STRENGHT OF CONCRETE**



# FACTORS AFFECTING STRENGTH OF CONCRETE

Water/cement ratio

Effective water in the mix

Gel/space ratio

Influence of aggregate/cement ratio on strength

Influence of properties of coarse aggregate

Effect of age on strength

Effect of temperature on strength

# FACTORS AFFECTING THE MEASURED STRENGTH

Loading rate

Size effect

Influence of moisture condition during test



# 1- WATER-CEMENT RATIO


- It is the ratio of the weight of water to the weight of cement in a concrete mix. This ratio **decides the strength and workability of concrete**.
- As per water-cement ratio, compressive strength of hardened concrete is inversely proportional to water cement ratio d hence it **depend upon the degree of compaction**.
- Compaction is a process accompanied by a decrease in air volume
- Insufficient compaction leading to air void content of 5% and 10 % results in loss of strength of 30% to 55% respectively.

When considering fully compacted concrete only: for mix proportioning purposes this is taken to mean that the hardened concrete contains about 1 % t of air voids. When concrete is fully compacted, its strength is taken to be inversely proportional to the water/cement ratio as shown in the following equation:

$$f_c = \frac{K_1}{K_2^{w/c}}$$

Where:

w/c : represents the water/cement ratio of the mix (originally taken by volume),  
 $K_1$  and  $K_2$  : are emprical constants.

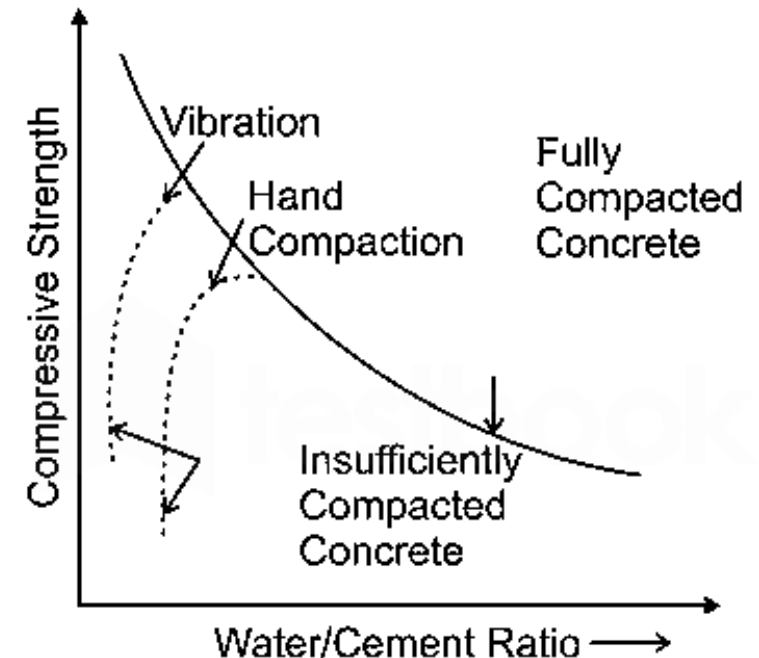

The relation between strength and water/cement ratio of concrete



## 2- Effective water in the mix


- We consider as effective that water which occupies space outside the aggregate particles when the gross volume of concrete becomes stabilized, i.e. approximately at the time of setting. Hence the terms effective, free, or net water/cement ratio.
- Generally, water in concrete consists: **(1) Added water to the mix, (2) Water that held by the aggregate at the time when it enters the mixers.**
- A part of the latter water is absorbed within the pore structure of the aggregate while some exists as free water on the surface of the aggregate and is therefore no different from the water added direct into the mixer.
- Conversely, when the aggregate is not saturated and some of its pores are therefore air filled, a part of the water added to the mix will be absorbed by the aggregate during the first half-hour or so after mixing. Under such circumstances the demarcation between absorbed and free water is a little difficult.

# 3- Gel/space ratio

- Gel space ratio define as the ratio of volume of the hydration to the sum of the volumes of the hydrated cement and of the capillary pores.

- In particular, strength at any water/cement ratio depends on:

- (1) Degree of hydration of cement.
- (2) Chemical and physical properties of cement.
- (3) Temperature at which hydration takes place.
- (4) Air content of the concrete.
- (5) Formation of cracks due to bleeding

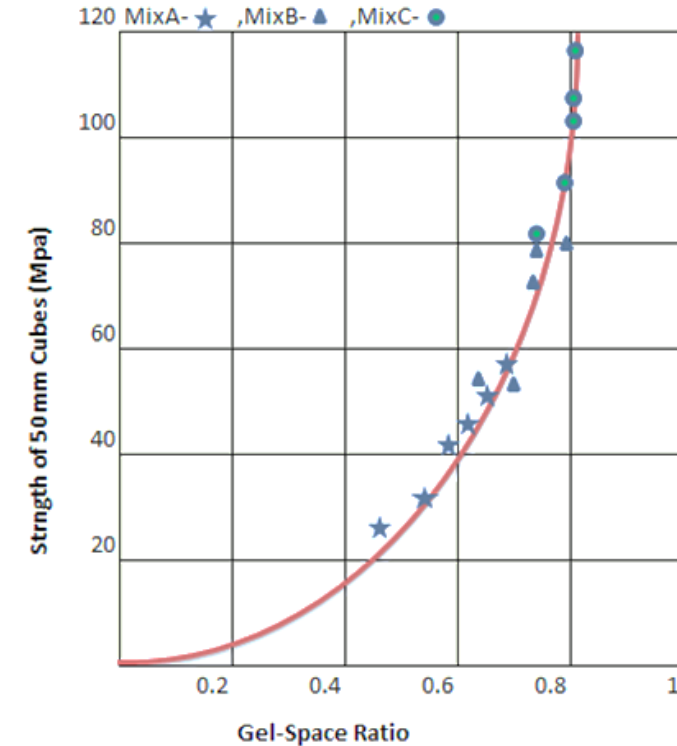

- It is more correct, therefore, to relate strength to the concentration of the solid products of hydration of cement in the space available for these products.
- **Power's experiment showed that the strength of concrete bears a specific relationship with the gel/space ratio. He found the relationship to be  $240 x^3$ , where  $x$  is the gel/space ratio and 240 represents the intrinsic strength of the gel in Mpa.**

# 4- Influence of aggregate/cement ratio on strength

- There is no doubt that the aggregate/ cement ratio, is only a secondary factor in the strength of concrete but it has been found that, for a constant water/cement ratio, a leaner mix leads to a higher strength.
- In certain cases, some water may be absorbed by the aggregate: a larger amount of aggregate absorbs a greater quantity of water, the effective water/ cement ratio being thus reduced.
- In other cases, a higher aggregate content would lead to lower shrinkage and lower bleeding, and therefore to less damage to the bond between the aggregate and the cement paste; likewise, the thermal changes caused by the heat of hydration of cement would be smaller.
- The total water content per cubic meter of concrete is lower in a leaner mix than in a rich one. As a result, in a leaner mix, the voids form a smaller fraction of the total volume of concrete, and it is these voids that have an adverse effect on strength.



# 5- Influence of properties of coarse aggregate

- Aggregates Are **The Key Factors** That Will Affect The Impact Strength Of Concrete
  - The properties of aggregate affect the cracking load, as distinct from an ultimate load, in compression and the flexural strength in the same manner that the relation between the two quantities is independent of the type of aggregate used.
  - On the other hand, the relation between the flexural and compressive strengths depends on the type of coarse aggregate because (except in high-strength concrete) the properties of aggregate, especially its **shape, size, and surface texture**, affect the ultimate strength in compression very much less than the strength in tension or the cracking load in compression.
- 
- The most common **size of aggregate** used in concrete is 20mm
  - coarse aggregate larger than 4.75 mm
  - fine aggregates below 4.75 mm.





# 5- Influence of properties of coarse aggregate

- In experimental concrete, entirely smooth coarse aggregate led to a lower compressive strength, typically by 10 % than when roughened.
- The influence of the type of coarse aggregate on the strength of concrete varies in magnitude and depends on the water/cement ratio of the mix:
  - a) For water/cement ratios below 0.4, the use of crushed aggregate has resulted in strengths up to 38 % higher than when gravel is used.
  - b) With an increase in the water/cement ratio to 0.5, the influence of aggregate falls off, presumably because the strength of the hydrated cement paste itself becomes paramount.
  - c) at a water/cement ratio of 0.65, no difference in the strengths of concretes made with crushed rock and gravel has observed.



# 6- Effect of age on strength

- The relation between the water/cement ratio and the strength of concrete applies to one type of cement and one age only, and also assumes wet curing conditions.
- On the other hand, the strength versus gel/space ratio relationship has a more general application because the amount of gel present in the cement paste at any time is itself a function of age and type of cement.
- The latter relation thus allows for the fact that different cements require a different length of time to produce the same quantity of gel.
- In concrete practice, the strength of concrete is traditionally characterized by the 28-day value, and some other properties of concrete are often referred to the 28-day strength. If, for some reason, the 28-day strength is to be estimated from the strength determined at an earlier age, say 7 days, then the relation between the 28-day and the 7-day strengths has to be established experimentally for the given mix.
- Strength at 28 days approximately 80-85% from the target strength.
- Strength at 28 days can estimate from strength at 7 days in relation.
- $\text{Strength at 28 days} = (1.3-1.7) \times \text{strength at 7 days}$ .



# 7- Effect of temperature on strength

- The rise in the curing temperature speeds up the chemical reactions of hydration and thus affects beneficially the early strength of concrete without any ill effects on the later strength.
- Higher temperature during and following the initial contact between cement and water reduces the length of the dormant period so that the overall structure of the hydrated cement paste becomes established very early.
- Although a higher temperature during placing and setting increases the very early strength, it may adversely affect the strength from about 7 days onwards. The explanation is that:
  1. rapid initial hydration appears to form products of a poorer physical structure, probably more porous, so that a proportion of the pores will always remain unfilled. It follows from the gel/space ratio rule, that this will lead to a lower strength compared with a less porous, though slowly hydrating, cement paste in which a high gel/space ratio will eventually be reached.
  2. at the high initial rate of hydration, there is insufficient time available for the diffusion of the products of hydration away from the cement particle and for a uniform precipitation in the interstitial space (as is the case at lower temperatures). As a result, a high concentration of the products of hydration is built up in the vicinity of the hydrating particles, and this retards the subsequent hydration and adversely affects the long-term strength.



# 7- Effect of temperature on strength

- For laboratory-made concrete, using ordinary or modified Portland cement, the optimum temperature is approximately 13 °C ; for rapid-hardening Portland cement it is about 4 °C .
- Beyond the initial period of setting and hardening the influence of temperature (within limits) accords with the maturity rule: a higher temperature accelerates the development of strength.
- The tests described so far were all made in the laboratory or under known conditions, but the behavior on site in a hot climate may not be the same.

## **There are some additional factors acting:**

- Ambient humidity.
- Direct radiation of the sun.
- Wind velocity.
- Method of curing.
- Temperature of concrete.
- Size of the member.



# FACTORS AFFECTING THE MEASURED STRENGTH

## (1) Loading rate

In general, the lower the rate of the loading, the lower the measured compressive strength. This may be attributed to the fact that :

- The slow rates of loading may allow more subcritical crack growth to occur, thus leading to the formation of larger flaws and hence a smaller apparent load.
- Slower loading rates allow more creep to occur, which will increase the amount of strain at a given load. When the limiting value of strain is reached, failure will occur.

## (2) Size effect :

The probability of having large deficiencies, such as void and crack, increases with size. Thus, smaller-size specimens will give higher apparent strengths.

## (3) Influence of moisture condition during test

The compressive strength decreases when the specimen is wet during testing. The loss of strength due to wetting of a compression test specimen is caused by the dilation of the cement gel by adsorbed water: the forces of cohesion of the solid particles are then decreased.

